

Polarization Selectivity of Aloof Beam EELS in One Dimensional ZnO Nanorods

Yao-Wen Yeh, Sobhit Singh, David Vanderbilt, and Philip E. Batson*

^aDepartment of Physics and Astronomy, Rutgers University, 136 Frelinghuysen Rd., Piscataway, 08854, NJ, USA

Abstract

Orientation dependent electronic properties of wurtzite zinc oxide nanorods are characterized by aloof beam electron energy-loss spectroscopy (EELS) carried out in a scanning transmission electron microscope (STEM). The two key crystal orientation differentiating transitions specific to the in-plane (13.0 eV) and out-of-plane (11.2 eV) directions with respect to the wurtzite structure are examined by first principles density-functional theory calculations. We note some degree of orientation dependence at the onset of direct band gap transition near 3.4 eV. We demonstrate that good polarization selectivity can be achieved by placing the electron probe at different locations around the specimen with increasing impact parameter while keeping the beam-specimen orientation fixed. The observed results are qualitatively elucidated in terms of the perpendicular electric fields generated by the fast electron (60 kV) used in the microscope. The fact that good polarization selectivity can be achieved by aloof beam EELS without the requirement of sample reorientation is an attractive aspect from the characterization method point of view in the STEM-EELS community.

Keywords: EELS, aloof beam, optical transitions, DFT, impact, scattering, wurtzite, anisotropy, ZnO, nanorods

1. Introduction

Scanning transmission electron microscope coupled electron energy-loss spectroscopy (STEM-EELS) plays an important role in the development and characterization of nanomaterials due to its high spatial resolution in both imaging and spectroscopy. In the more straightforward intersecting beam-specimen configuration where the interaction is dominated by impact scattering, high resolution STEM-EELS is able to probe local material properties such as interface states [1] and single-atom dopant electronic properties [2], and even vibrational properties [3, 4, 5] aided by recent development in energy monochromators [6]. Typically, these high spatial resolution STEM-EELS experiments are carried out with a focused electron probe with a large convergence semi-angle (α), which allows the incident electrons to excite the specimen with significant momentum transfer. With a common circular collection aperture used in the on-axis

arrangement, the acquired transmitted signals lead to the so called momentum integrated energy-loss spectra [4, 7]. When the specimen of interest has complex electronic and phonon structures in the reciprocal space, the resulting EELS spectra would also reflect the structural complexity, which can make it difficult to fully interpret the observed spectra without prior knowledge of the material.

Meanwhile, in the aloof beam (non-intersecting probe-specimen) configuration where the interaction is dominated by dipole scattering, the electron beam behaves as a near-field spectroscopy probe [8] and can be used to study long range electric field (**E**) related phenomena such as vibrational properties [9, 10], surface plasmon-polaritons in metal and doped-semiconductor nanostructures [11, 12, 13], and surface phonon-polaritons in insulating nanostructures [14, 15]. Recently, Rez *et al.* [16] and Crozier [17] discussed the non-destructive nature of the aloof beam EELS and expanded its applications in studying vibrational and electronic properties for electron beam sensitive materials. In addition to the non-destructive characterization, Radtke *et al.* [10] have fur-

*corresponding author: batson@physics.rutgers.edu

ther applied aloof beam EELS to study polarization dependent vibrational properties of anisotropic materials demonstrating that good polarization selectivity can be achieved by aloof beam EELS. We note that orientation dependent anisotropic properties have traditionally been measured in the beam-specimen intersecting configuration with small beam convergence ($\alpha < 0.5$ mrad) in the past. [18, 19, 20]

Here, we explore the potential application of aloof beam EELS to characterize the polarization-dependent electronic structures of uniaxial crystals in scenarios where specimen reorientation is challenging to achieve by the microscope goniometer. In particular, we study one dimensional wurtzite zinc oxide (w-ZnO) nanorods in a fixed beam-to-specimen orientation, compare the results obtained with the intersecting and aloof beam configurations, and demonstrate that the aloof beam EELS offers good polarization selectivity when the impact parameter, *i.e.*, specimen-to-probe distance, is large enough (~ 6 nm). The prominent anisotropic features that differentiate the in-plane (\perp to c axis) and out-of-plane (\parallel to c axis) responses of w-ZnO nanorods are examined by first-principles density-functional theory (DFT) calculations. Our results assert that the previously debated transition at 11.2 eV in w-ZnO is not due to a surface plasmon [21, 22], but instead corresponds to an orientation-dependent interband transition from the occupied Zn-3d states to the unoccupied O-2p_z states near the zone center [23]. Finally, we discuss the aloof beam results in terms of the electric fields associated with the excitation source (incident electrons) rather than the dielectric function that describes the response to an external perturbation. This approach provides qualitative but intuitive understanding of the results. Moreover, the fact that good polarization selectivity can be achieved by aloof beam EELS without specimen reorientation is another attractive aspect to the technique, as many technologically important materials can be anisotropic and have large aspect ratios [24, 25].

2. Materials and methods

w-ZnO nanorods were synthesized via the hydrothermal route described by Cheng and Samulski [26]. The two starting solutions were obtained by mixing (1) 0.1M of zinc acetate dihydrate ($\text{Zn}(\text{Ac})_2 \cdot 2\text{H}_2\text{O}$) in methanol and (2) 0.5M of sodium hydroxide (NaOH) in ethanol. 60

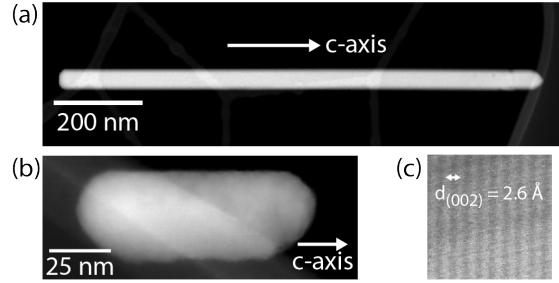


Figure 1: Annular dark-field STEM image of a single suspended (a) long and (b) short ZnO nanorods on lacey carbon support. The long axis of the nanorod corresponds to c axis of w-ZnO. (c) High resolution image of (002) lattice fringes with the spacing of 2.6 Å.

ml of of the mixed solution (1:1 volume ratio) was then transferred to a Teflon-lined stainless steel autoclave and heated at 150 °C for 8 hours. After the autoclave was cooled to room temperature, the white precipitates containing ZnO nanorods were washed with de-ionized water four times and dried at 60 °C in an oven overnight. The dried powder was then annealed in air at 400 °C for 1 hour to improve its crystallinity. The electron microscopy sample was prepared by first dispersing the annealed ZnO powder in ethanol via sonication and the sample containing solution was then drop cast onto a lacey carbon coated copper grid.

The synthesized nanorods have lengths that range from 90 to 1200 nm and widths that range from 35 to 40 nm. Typical long and short synthesized nanorods are shown in Figs. 1(a) and 1(b), respectively. As reported by Cheng and Samulski [26] the rods preferentially grow along the c axis. Regardless of the rod lengths, the c axis of w-ZnO is always along the rod axis as confirmed by the high resolution image shown in Fig 1(c) where $d_{002} = 2.6$ Å was observed.

The STEM-EELS experiments reported here were carried out in a monochromated Nion UltraSTEM operating at 60 kV. The beam convergence and EELS collection semi-angles were set at 30 and 16 mrad, respectively. The energy resolution for the spectra is 0.13 eV according to the full-width-half-maximum of the zero-loss peak.

DFT calculations were performed using the Projector Augmented Wave (PAW) method as implemented in the Vienna Ab initio Simulation Package (VASP) [27, 28, 29]. Twelve and six valence electrons were considered

in the zinc and oxygen PAW pseudopotentials, respectively. The Perdew-Burke-Ernzerhof generalized-gradient approximation for solids (GGA-PBEsol) was used to compute the exchange-correlation functional [30]. The reciprocal space was sampled using a Γ -centered k -mesh of size $16 \times 16 \times 10$ together with a kinetic energy cutoff of 650 eV for plane waves. The energy convergence and force convergence criteria were set to 10^{-8} eV and 10^{-4} eV/Å, respectively.

All the DFT calculations were carried out in a four-atom hexagonal unit cell of w-ZnO (space group: $P6_3mc$). The GGA-PBEsol optimized lattice parameters are $a = b = 3.236$ Å, and $c = 5.223$ Å, which are in good agreement with the experimental data [31, 32]. The employed DFT predicts w-ZnO to be a direct band gap semiconductor with an energy band gap of 0.7 eV at Γ . We apply a scissor operation of 2.7 eV to obtain the reported experimental bandgap of 3.4 eV in w-ZnO [31, 32, 33, 34]. The calculated electronic bandstructure (in particular, the structure of the conduction bands and valence bands near the Fermi level) matches reasonably well with the previously reported hybrid and quasi-particle GW calculations [35, 36, 37, 38, 39, 40, 41, 42, 43]. The frequency-dependent imaginary dielectric function $\epsilon_2(\omega)$ was calculated using the method described in Ref. [44]. The convergence of $\epsilon_2(\omega)$ was ensured by increasing the number of empty conduction bands. The calculated $\epsilon_2(\omega)$ is in good agreement with the previous studies [45, 35, 46, 47, 48, 36, 38] and gives a good description of the recorded EELS spectra in this work.

3. Results and discussion

w-ZnO is a uniaxial material of hexagonal structure and it possesses two sets of dielectric properties - one associated to the in-plane direction (a and b axes) and the other associated to the out-of-plane (c axis) direction. The oxygen $2p_{xy}$ (in-plane) and $2p_z$ (out-of-plane) orbitals play an important role in governing the anisotropic electronic properties of w-ZnO. Our results, presented below, as well as previous studies [31, 49, 50, 45, 51, 35, 46, 47, 48, 36, 38], suggest that there are several distinct optical (dipole-dipole) interband transitions in w-ZnO at energies of ~ 3.4 , 9.1, 11.2, 13.0, 13.5, and 14.8 eV, as listed in Table 1. Although the transitions at ~ 3.4 , 9.1,

and 13.5 eV are well documented in the existing literature [31, 49, 50, 45, 51, 35, 46, 47, 48, 36, 38], less is known about the other listed transitions. Notably, the transitions at 9.1, 13.5, and 14.8 eV are not very sensitive to the polarization orientation, as these are common to both the in-plane and out-of-plane polarization orientations of the \mathbf{E} -field. In contrast, the transitions at 3.4, 3.5, 11.2, and 13.0 eV exhibit strong orientation dependence due to the anisotropic nature of the $O-2p_{xy}$ and $O-2p_z$ orbitals in w-ZnO. Since the energy difference between the transitions at 3.4 eV ($\mathbf{E} \perp \mathbf{c}$) and 3.5 eV ($\mathbf{E} \parallel \mathbf{c}$) is almost the same as the energy resolution of our EELS measurements, we cannot unambiguously distinguish them, although we do notice the signatures of the orientation dependence of these transitions. However, our EELS measurements clearly distinguish the orientation-dependent transitions at 11.2 eV ($\mathbf{E} \perp \mathbf{c}$) and 13.0 eV ($\mathbf{E} \parallel \mathbf{c}$).

Table 1: Calculated optical transitions below 15.0 eV, from the occupied to unoccupied states near the Fermi level, and their polarization orientation with respect to the c axis in w-ZnO

Energy (eV)	Orientation	Assignment
3.4	\perp	$O-2p_{xy} \rightarrow Zn-3s$
3.5	\parallel	$O-2p_z \rightarrow Zn-3s$
9.1	$\perp \& \parallel$	$Zn-3d \rightarrow O-2p$
11.2	\parallel	$Zn-3d \rightarrow O-2p_z$
13.0	\perp	$Zn-3d \rightarrow O-2p_{xy}$
13.5	$\perp \& \parallel$	$O-2p \rightarrow Zn-3s$
14.8	$\perp \& \parallel$	$Zn-3d \rightarrow \{O-2p, Zn-3s\}$
	$\perp \& \parallel$	$O-2p \rightarrow \{Zn-3d, Zn-3s\}$

In our experiments, the ZnO nanorod is oriented such that the incident electron beam is perpendicular to the crystal c axis. Fig. 2 shows the EELS spectrum of ZnO obtained using the specimen-intersecting beam and the inset shows the scattering geometry. The three most apparent spectral features are the direct band gap near 3.4 eV, $Zn-3d$ to $O-2p$ transition around 9.1 eV, and the bulk plasmon at 18.8 eV, which are consistent with the previous observations [21, 22, 51, 50, 23]. With the large beam con-

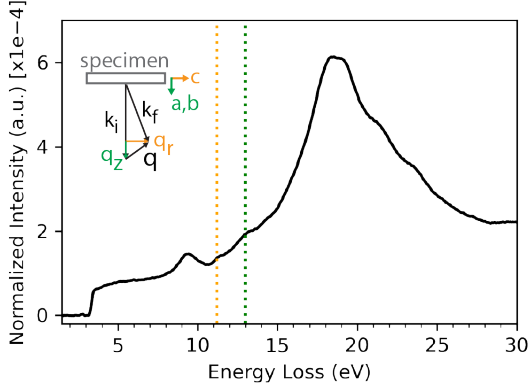


Figure 2: Valence EELS spectrum acquired with the beam intersecting configuration after Fourier-log deconvolution [52] and background removal. Three major peaks are the onset of the band gap around 3.4 eV, Zn-3d to O-2p transition around 9.1 eV, and the bulk plasmon at 18.8 eV. While not being immediately obvious, the orientation specific features can be seen around 11.2 eV (out-of-plane) and 13.0 eV (in-plane) as guided by the dotted orange and green lines, respectively. The inset shows the scattering geometry with $\hat{c} \parallel \hat{q}_r$ and \hat{a} and $\hat{b} \parallel \hat{q}_z$.

vergent angle ($\alpha = 30$ mrad) used in the present study, the beam is able to excite transitions with polarization along both the parallel (a and b axes) and perpendicular (c axis) to the beam (crystal) directions.

In conjunction with the large incident beam convergence angle, the moderate EELS collection angle ($\beta = 16$ mrad) used in the present study leads to momentum integrated EELS [7]. Consequently, the orientation-specific 11.2 ($\parallel c$) and 13.0 eV ($\perp c$) transitions are always observed in the spectrum regardless of where the beam is placed, as long as the beam intersects the sample. However, the poor polarization selectivity observed in the intersecting configuration makes it impractical in studying orientation specific features. We should note that the scattered signals being collected can be further restricted to the beam parallel direction and achieve decent polarization selectivity in the intersection configuration by using a smaller aperture to reduce the collection angle [53]. However, such small aperture is not available in our current microscope setup. In addition, restricting momentum transfer causes unavoidable uncertainty-principle driven spread in the area that is sampled, degrading the desired spatial resolution of the measurement using the STEM.

In addition, due to the considerable momentum trans-

fer ($\vec{q} = \vec{q}_r + \vec{q}_z$) in the intersecting scattering configuration, the transitions around 11.2, 13.0, 13.5, and 14.8 eV appear as minor humps which are partly obscured by the nearby transitions and the bulk plasmon. Moreover, the 11.2 eV hump was misinterpreted as a surface plasmon in the past [21, 22]. In the present study, we focus on the anisotropic features of w-ZnO, and for more detailed spectral feature assignments we refer the readers to Refs. [51, 23].

To explore the polarization selectivity of the aloof beam EELS while keeping the rod orientation fixed, we acquired two sets of data points - one in the vicinity of the rod tip and the other in the vicinity of the lateral-middle position of the rod. Each set contains spectra acquired at three different impact parameters (d) of 2, 4, and 6 nm along the directions indicated by the orange and green arrows, as shown in Fig. 3(a). The acquired spectra near the lateral-middle and the tip of the rod are shown in Figs. 3(b) and 3(c), respectively. Consistent with the calculated transitions listed in Table 1, the not very orientation-specific transitions around 3.4 eV and the 9.1 and 13.5 eV peaks are observed in both aloof beam data sets, and the broad peak around 16.0 eV is the surface plasmon [23]. We note that the last non-orientation specific transition at 14.8 eV is overshadowed by the broad surface plasmon peak, making it difficult to identify.

At small impact parameter (*i.e.*, $d = 2$ nm), both the 11.2 eV and 13.0 eV transitions are visible in both sets. However, as the impact parameter increases, the 11.2 eV and 13.0 eV transitions remain significant only when the electron beam is placed near the tip and lateral-middle position of the rod, respectively. Therefore, good polarization selectivity is achieved when $b = 6$ nm, despite the fact that the beam-parallel electric field (\perp to the specimen c axis) is always present. Unlike in Ref. [10], where the polarization-dependent spectra were acquired with two different beam-to-specimen orientations, the aloof beam spectra presented here were acquired with the same beam-to-specimen orientation but at different locations and different values of impact parameter.

To understand the observed aloof beam EELS results, we turn our attention to the electric fields generated by the incident electron, since the material response (induced dipole field) also scales with the external perturbation magnitude. The fast electrons (60 keV) used here can be considered as a broadband electromagnetic

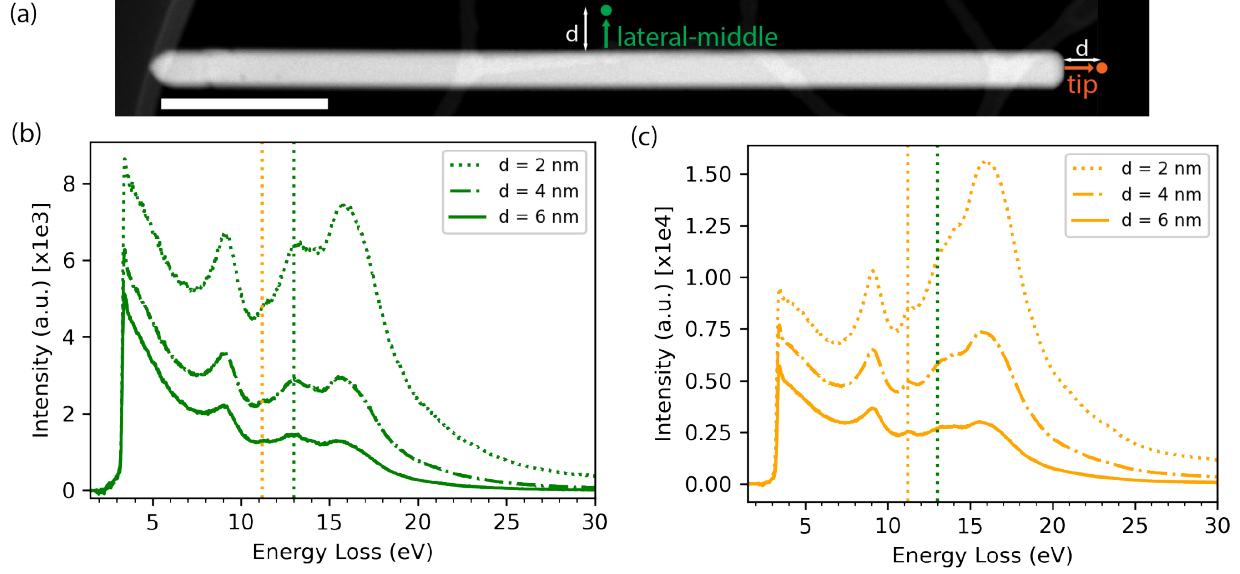


Figure 3: (a) The high annular dark field image of a 1100 by 40 nm ZnO nanorod (scale bar: 200 nm) where the green and orange dots indicate the electron beam locations where the aloof beam spectra were acquired. Three spectra were acquired at impact parameters of 2, 4, and 6 nm (b) along the green arrow near the lateral-middle position of the rod and (c) along the orange arrow near the rod tip. The dotted vertical line at 11.2 and 13.0 eV indicate the key anisotropic transitions that are specific to the direction parallel and perpendicular to the c axis, respectively.

source [54, 55] producing electric fields in the frequency domain that can be broken down into two parts - one being perpendicular to the incident electron beam direction E_R and the other being parallel to the beam E_z [54, 55, 56] as follows

$$E_R(x, y, z, \omega) = -\frac{2e\omega}{Rv^2\gamma} e^{i\omega z/v} K_1\left(\frac{\omega R}{v\gamma}\right) [(x-d)\vec{x} + y\vec{y}], \quad (1)$$

$$E_z(x, y, z, \omega) = i\frac{2e\omega}{Rv^2\gamma^2} e^{i\omega z/v} K_0\left(\frac{\omega R}{v\gamma}\right) \vec{z}. \quad (2)$$

Here (x, y, z) is the observation location in the lab frame, e is the electric charge, ω is the angular frequency, d is the impact parameter, K_n is the modified Bessel function of second kind with index n , $R^2 = (x-d)^2 + y^2$, v is the electron speed, $\gamma = [1 - (v/c)^2]^{-1/2}$ is the Lorentz factor, and c is the speed of light in vacuum. On the other hand, we would also like to point out that the induced dipole field exerts forces on the incident electrons and wraps around the nanorod, occupying a three dimensional volume as illustrated in Ref. [53]. The induced

field components perpendicular and parallel to the incident electrons are responsible for the electron deflection and energy loss, respectively.

We now focus our attention on the field distributions in the plane perpendicular to the beam direction (Eq. 1), as this component is larger than the parallel one [7, 16, 10] and contributes more to the overall electron-specimen interactions in the valence energy range considered here. As shown in Figs. 4(a) and 4(b), we plot the perpendicular electric field distributions (Eq. 1) at 11.2 eV within the nanorod area (delineated by the grey dotted line) when the beam is placed outside the lateral-middle and the tip of the rod, respectively. The x and y coordinates used here are referenced to the long (c axis) and short axes of the ZnO crystal, and we refer the electric field components parallel and perpendicular to the c axis as E_{\parallel} and E_{\perp} , respectively. It can be seen that the resultant field becomes more directional toward the beam location when the beam is placed further away from the specimen.

To visualize how the resultant field becomes more ‘collimated’ in the plane perpendicular to the beam direction

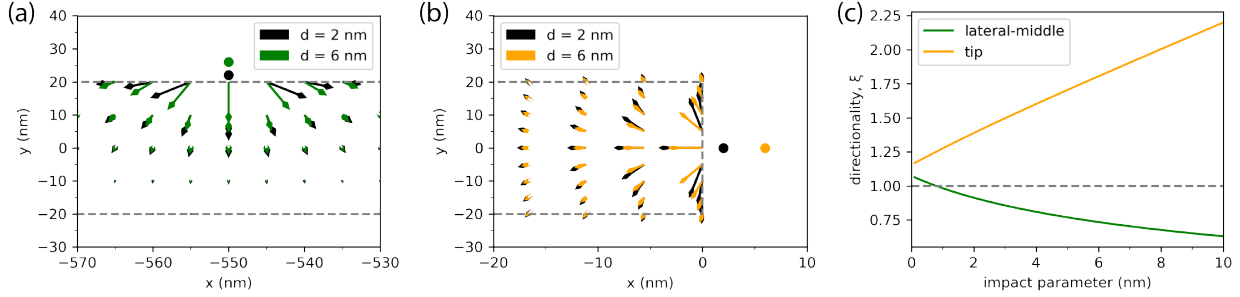


Figure 4: Electric field distributions, $E_R(R)$ generated by the fast electron at 11.2 eV within the nanorod when the aloof beam is placed near (a) the lateral-middle and (b) the tip of the rod. The black and green (orange) circles represent the electron beam positions at the impact parameters of 2 and 6 nm, respectively. The nanorod area is delineated by the grey dashed lines. The fields are more ‘collimated’ toward the beam location as the impact parameter increases from 2 to 6 nm. The direction of the field arrows is reversed to avoid overlapping with the circles. (c) The directionality parameter versus the impact parameter near the lateral-middle (green) and the tip (orange) of the rod.

as the impact parameter increases, we define a directionality parameter $\xi = \Sigma(E_{\parallel})/\Sigma(E_{\perp})$, where $\Sigma(E_{\parallel})$ and $\Sigma(E_{\perp})$ are sums over a representative sampling of points within the nanorod. Figure 4(c) shows the variation of ξ as a function of the impact parameter d . It is found that the electron beam generates electric fields that are more parallel to the c axis near the tip (orange curve) than the lateral-middle (green curve) position of the rod. **To put it more generally, when the specimen is placed on one side next to the beam with the extent no larger than its corresponding half-space, the fields that are generated by the beam and felt by the specimen are inherently asymmetric and directional in the aloof beam configuration. The larger the impact parameter, the more the aloof beam EELS resembles polarized optical spectroscopy.** Therefore, in the case of w-ZnO, the 11.2 eV feature is only noticeable at large impact parameter near the tip but not at the lateral-middle position of the rod. A similar argument can be extended for the 13.0 eV feature.

To accentuate the anisotropic features of w-ZnO in the aloof spectra, we scale the spectra with respect to the Bessel function part of Eq. 1 and normalize the intensity around the band gap as the dielectric functions around the gap have very similar values. As shown in Fig. 5(a), the normalization reduces the low energy intensities in contrast to Figs. 3(b) and 3(c) and facilitates visualization of the orientation-specific transitions at 11.2 eV ($E \parallel c$) and 13.0 eV ($E \perp c$) near the tip (orange) and the lateral-middle (green) positions, respectively.

In order to pin down the nature of the observed optical transitions, we employ DFT calculations as detailed in the methods section. The calculated polarization-orientation dependent imaginary dielectric function $\epsilon_2(\omega)$, which contains full details of the optical-transition matrix elements and the interband absorption processes, is in remarkable agreement with the recorded EELS spectra for both orientations, as shown in Fig. 5(b). Magenta and purple arrows respectively mark the orientation specific $E \parallel c$ and $E \perp c$ transitions, respectively, whereas, the black arrows mark the transitions that are not strongly orientation sensitive. The orbital-resolved electronic bandstructure, shown in Fig. 5(c), further facilitates the identification of the observed interband transitions from occupied to unoccupied states, as discussed below.

We note that the onset of the direct band gap transition near 3.4 eV, although marked using a black arrow, is technically orientation dependent due to the splitting of the O-2p states into a subset of O-2 p_{xy} and O-2 p_z states at the valence band maximum (see Fig. 6(b) in Appendix). This occurs due to the asymmetry of the wurtzite structure, which reduces the energy of the O-2 p_z orbitals by ~ 0.1 eV with respect to the valence band maximum formed by O-2 p_{xy} orbitals. Therefore, in principle, the onset of direct band gap transitions for $E \perp c$ (O-2 $p_{xy} \rightarrow \text{Zn-}3s$) and $E \parallel c$ (O-2 $p_z \rightarrow \text{Zn-}3s$) should occur near 3.4 and 3.5 eV, respectively. Although this feature is well captured in our DFT calculations, it is only faintly visible in our EELS spectra due to the limited energy resolution of our

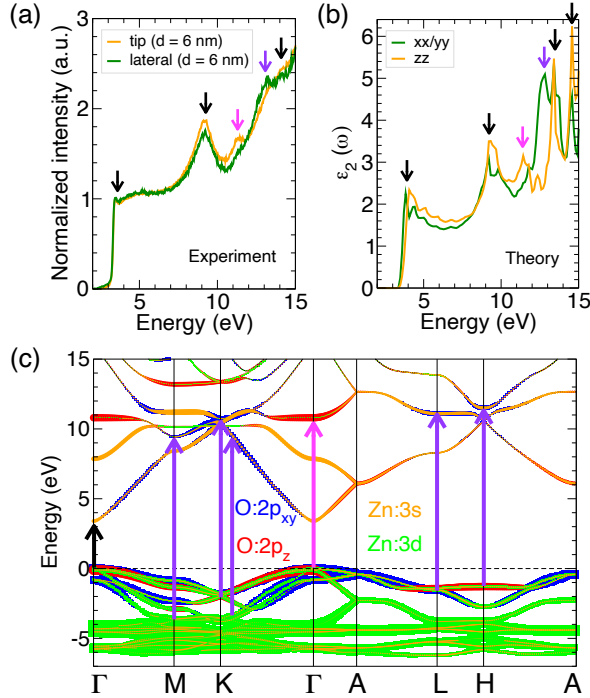


Figure 5: (a) Normalized aloof beam spectra ($d = 6$ nm) acquired near the tip (orange) and the lateral-middle position (green) of the rod. The two anisotropic features at 11.2 eV ($E \parallel c$) and around 13.0 eV ($E \perp c$), marked using magenta and purple arrows, are differentiated near the tip and the lateral-middle position of the rod, respectively. The observed spectra demonstrate good polarization selectivity of the aloof beam EELS. (b) Polarization-orientation dependent imaginary dielectric functions, $\epsilon_2(\omega)$, calculated along xx/yy ($E \perp c$) and zz ($E \parallel c$) directions. The arrows mark the transitions of interest. (c) DFT calculated orbital-resolved electronic band structure of w-ZnO. Magenta and purple arrows depict the observed inter-band optical transitions at 11.2 eV ($E \parallel c$) and near 13.0 eV ($E \perp c$), whereas black arrow denotes the direct band gap transition at 3.4 eV.

measurements (0.13 eV).

The key orientation-dependent transitions at 11.2 and 13.0 eV are identified as $\text{Zn-3d} \rightarrow \text{O-2p}_z$ near Γ and $\text{Zn-3d} \rightarrow \text{O-2p}_{xy}$ near the boundaries of the hexagonal Brillouin zone (BZ), respectively. On the other hand, orientation-independent transitions at 9.1 and 13.5 eV are identified as $\text{Zn-3d} \rightarrow \text{O-2p}$ and $\text{O-2p} \rightarrow \text{Zn-3s}$, respectively. Our DFT calculations reveal the presence of another orientation-independent transition at 14.8 eV, which could not be distinctly observed in the recorded EELS spectra. It appears as a minor hump, primarily due to the

presence of the nearby and broad surface plasmon. This transition is attributed to the dipole-dipole transition from occupied Zn-3d to unoccupied $\{\text{O-2p}, \text{Zn-3s}\}$ and occupied O-2p to unoccupied $\{\text{Zn-3d}, \text{Zn-3s}\}$ states. Some of the above-mentioned transitions occur at various k -points within the hexagonal BZ and between different sets of occupied and unoccupied bands. In Figs. 6 and 7, we made an attempt to mark some of these transitions having maximum optical-transition matrix elements using arrows. A summary of these transitions is provided in Table 1.

Finally, we note that as indicated by Eq. 1, the field strength decreases rapidly with increasing impact parameter or with increasing energy. This means that while the aloof beam EELS may be a practical means to study excitation in the vibrational and the valence energy ranges, this may not be the case for the high energy core loss region and when the impact parameter is too large.

4. Summary

We have characterized the electronic structures of single crystal w-ZnO nanorods by both intersecting and aloof beam configurations with a focused electron beam ($\alpha = 30$ mrad) and moderate collection angle ($\beta = 16$ mrad). The key anisotropic features of w-ZnO that are specific to the in-plane and out-of-plane directions were identified by DFT calculations. It was demonstrated experimentally that when keeping the beam-to-specimen orientation fixed, good polarization selectivity can only be achieved by the aloof beam configuration, not the intersecting one. We found that the good polarization selectivity brought by the aloof beam can be explained by analyzing the perpendicular component of the electric fields (Eq. 1) generated by the fast electron used in the STEM-EELS experiments. The fact that the field directionality can be tuned by varying the impact parameter can be very useful in reducing spectral complexity and characterizing anisotropic nanomaterials such as the w-ZnO nanorods presented here.

Acknowledgement

P.B. acknowledge the financial supports of U.S. Department of Energy, Office of Science, Basic Energy Sciences under award no. DE-SC0005132. D.V. acknowledges the support from National Science Foundation grant DMR-1954856. We also thank N. Dellby and M. Hoffman for

discussions regarding the optical configuration of the microscope.

5. Appendix

Here we provide orbital-resolved electronic band structures marked with orientation-dependent (Fig. 6) and orientation-independent (Fig. 7) interband transitions. Only selected transitions having large optical-transition matrix elements are marked using arrows. There are numerous other transitions with relatively smaller transition probability which are not marked for the sake of clarity. Zn-3s and Zn-3d orbitals are depicted in orange and green colors, whereas O-2p_{xy} and O-2p_z orbitals are shown in blue and red colors, respectively, in all orbital-resolved band structures.

References

- [1] D. A. Muller, T. Sorsch, S. Moccio, F. Baumann, K. Evans-Lutterodt, G. Timp, The electronic structure at the atomic scale of ultrathin gate oxides, *Nature* 399 (6738) (1999) 758–761.
- [2] Q. M. Ramasse, C. R. Seabourne, D.-M. Kepaptsoglou, R. Zan, U. Bangert, A. J. Scott, Probing the bonding and electronic structure of single atom dopants in graphene with electron energy loss spectroscopy, *Nano Letters* 13 (10) (2013) 4989–4995.
- [3] M. J. Lagos, P. E. Batson, Thermometry with sub-nanometer resolution in the electron microscope using the principle of detailed balancing, *Nano letters* 18 (7) (2018) 4556–4563.
- [4] K. Venkatraman, B. D. Levin, K. March, P. Rez, P. A. Crozier, Vibrational spectroscopy at atomic resolution with electron impact scattering, *Nature Physics* 15 (12) (2019) 1237–1241.
- [5] F. Hage, G. Radtke, D. Kepaptsoglou, M. Lazzeri, Q. Ramasse, Single-atom vibrational spectroscopy in the scanning transmission electron microscope, *Science* 367 (6482) (2020) 1124–1127.
- [6] O. L. Krivanek, T. C. Lovejoy, N. Dellby, T. Aoki, R. Carpenter, P. Rez, E. Soignard, J. Zhu, P. E. Batson, M. J. Lagos, et al., Vibrational spectroscopy in the electron microscope, *Nature* 514 (7521) (2014) 209–212.
- [7] B. Rafferty, L. Brown, Direct and indirect transitions in the region of the band gap using electron-energy-loss spectroscopy, *Physical Review B* 58 (16) (1998) 10326.
- [8] H. Cohen, T. Maniv, R. Tenne, Y. R. Hacohen, O. Stephan, C. Colliex, Near-field electron energy

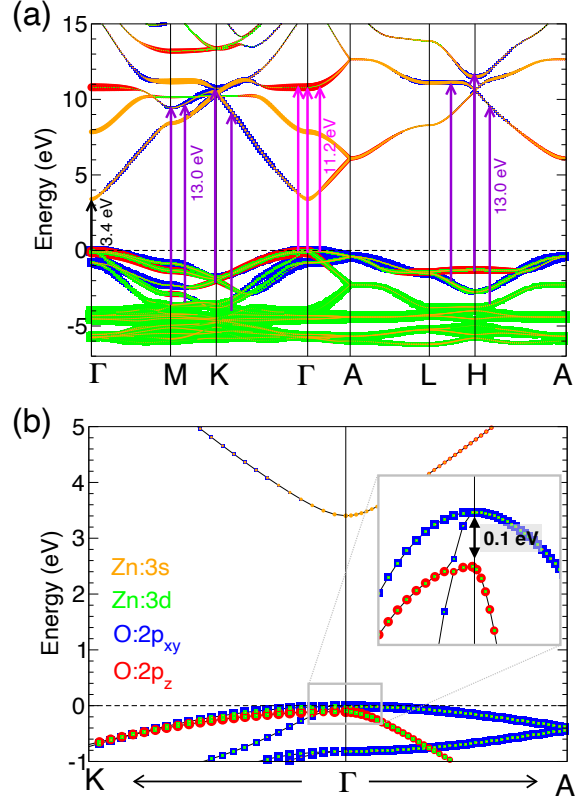


Figure 6: (a) Orientation-dependent interband transitions at 3.4, 11.2, and 13.0 eV marked using arrows in the orbital-resolved electronic band structure of w-ZnO. (b) An enlarged of bands near the Fermi level at zone center Γ . Inset shows a further amplification of valence band maximum near Γ . Crystal-field induced splitting of O-2p_{xy} and O-2p_z orbitals can be noticed.

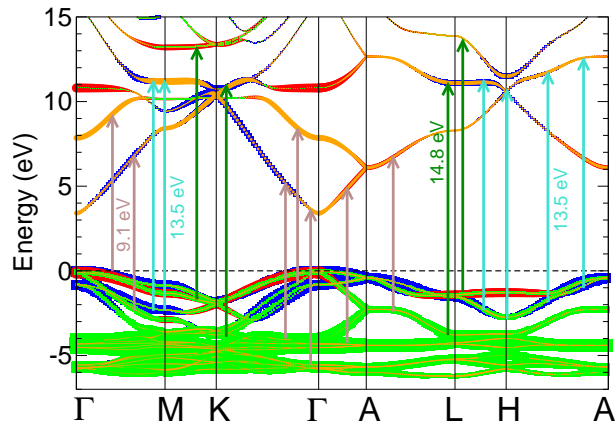


Figure 7: Orientation-independent interband transitions at 9.1, 13.5, and 14.8 eV marked using arrows in the orbital-resolved electronic band structure of w-ZnO. Only selected transitions having large optical-transition matrix elements are marked.

- loss spectroscopy of nanoparticles, *Physical review letters* 80 (4) (1998) 782.
- [9] G. Radtke, D. Taverna, M. Lazzeri, E. Balan, First-principles vibrational electron energy loss spectroscopy of β -guanine, *Phys. Rev. Lett.* 119 (2017) 027402.
- [10] G. Radtke, D. Taverna, N. Menguy, S. Pandolfi, A. Courac, Y. Le Godec, O. L. Krivanek, T. C. Lovejoy, Polarization selectivity in vibrational electron-energy-loss spectroscopy, *Phys. Rev. Lett.* 123 (2019) 256001.
- [11] P. Batson, A new surface plasmon resonance in clusters of small aluminum spheres, *Ultramicroscopy* 9 (3) (1982) 277–282.
- [12] D. Rossouw, G. A. Botton, Plasmonic response of bent silver nanowires for nanophotonic sub-wavelength waveguiding, *Physical Review Letters* 110 (6) (2013) 066801.
- [13] H. Yang, E. L. Garfunkel, P. E. Batson, Probing free carrier plasmons in doped semiconductors using spatially resolved electron energy loss spectroscopy, *Phys. Rev. B* 102 (2020) 205427.
- [14] M. J. Lagos, A. Trügler, U. Hohenester, P. E. Batson, Mapping vibrational surface and bulk modes in a single nanocube, *Nature* 543 (7646) (2017) 529–532.
- [15] R. Qi, R. Wang, Y. Li, Y. Sun, S. Chen, B. Han, N. Li, Q. Zhang, X. Liu, D. Yu, et al., Probing far-infrared surface phonon polaritons in semiconductor nanostructures at nanoscale, *Nano letters* 19 (8) (2019) 5070–5076.
- [16] P. Rez, T. Aoki, K. March, D. Gur, O. L. Krivanek, N. Dellby, T. C. Lovejoy, S. G. Wolf, H. Cohen, Damage-free vibrational spectroscopy of biological materials in the electron microscope, *Nature communications* 7 (1) (2016) 1–8.
- [17] P. A. Crozier, Vibrational and valence aloof beam eels: A potential tool for nondestructive characterization of nanoparticle surfaces, *Ultramicroscopy* 180 (2017) 104–114, Ondrej Krivanek: A research life in EELS and aberration corrected STEM.
- [18] R. D. Leapman, J. Silcox, Orientation dependence of core edges in electron-energy-loss spectra from anisotropic materials, *Phys. Rev. Lett.* 42 (1979) 1361–1364.
- [19] R. D. Leapman, P. L. Fejes, J. Silcox, Orientation dependence of core edges from anisotropic materials determined by inelastic scattering of fast electrons, *Phys. Rev. B* 28 (1983) 2361–2373.
- [20] R. Arenal, M. Kociak, N. J. Zaluzec, High-angular-resolution electron energy loss spectroscopy of hexagonal boron nitride, *Applied Physics Letters* 90 (20) (2007) 204105. doi:10.1063/1.2740185.
- [21] J. Wang, X. An, Q. Li, R. Egerton, Size-dependent electronic structures of ZnO nanowires, *Applied Physics Letters* 86 (20) (2005) 201911.
- [22] J. Wang, Q. Li, R. Egerton, Probing the electronic structure of ZnO nanowires by valence electron energy loss spectroscopy, *Micron* 38 (4) (2007) 346–353.

- [23] M. R. S. Huang, R. Erni, H.-Y. Lin, R.-C. Wang, C.-P. Liu, Characterization of wurtzite zno using valence electron energy loss spectroscopy, *Phys. Rev. B* 84 (2011) 155203.
- [24] Y. Xia, P. Yang, Y. Sun, Y. Wu, B. Mayers, B. Gates, Y. Yin, F. Kim, H. Yan, One-dimensional nanostructures: synthesis, characterization, and applications, *Advanced materials* 15 (5) (2003) 353–389.
- [25] P. R. Sajanlal, T. S. Sreeprasad, A. K. Samal, T. Pradeep, Anisotropic nanomaterials: structure, growth, assembly, and functions, *Nano reviews* 2 (1) (2011) 5883.
- [26] B. Cheng, E. T. Samulski, Hydrothermal synthesis of one-dimensional zno nanostructures with different aspect ratios, *Chem. Commun.* (2004) 986–987.
- [27] G. Kresse, J. Furthmüller, Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set, *Phys. Rev. B* 54 (1996) 11169–11186.
- [28] G. Kresse, J. Furthmüller, Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set, *Computational Materials Science* 6 (1) (1996) 15 – 50.
- [29] G. Kresse, D. Joubert, From ultrasoft pseudopotentials to the projector augmented-wave method, *Phys. Rev. B* 59 (1999) 1758–1775.
- [30] J. P. Perdew, A. Ruzsinszky, G. I. Csonka, O. A. Vydrov, G. E. Scuseria, L. A. Constantin, X. Zhou, K. Burke, Restoring the density-gradient expansion for exchange in solids and surfaces, *Phys. Rev. Lett.* 100 (2008) 136406.
- [31] S. Adachi, *Optical Constants of Crystalline and Amorphous Semiconductors*, 1st Edition, Springer Science+Business Media, LLC., New York, New York, 1999.
- [32] Z. L. Wang, Zinc oxide nanostructures: growth, properties and applications, *Journal of Physics: Condensed Matter* 16 (25) (2004) R829–R858.
- [33] L. Franklin, C. Ekuma, G. Zhao, D. Bagayoko, Density functional theory description of electronic properties of wurtzite zinc oxide, *Journal of Physics and Chemistry of Solids* 74 (5) (2013) 729–736. doi:<https://doi.org/10.1016/j.jpcs.2013.01.013>.
- [34] H. Nejati-pour, M. Dadsetani, Electronic structures of $\text{Zn}_x\text{S}_{1-x}$ ($x=0$ and s) nanosheets from first-principles energy loss near edge structure studies, *Journal of Electron Spectroscopy and Related Phenomena* 203 (2015) 14–24. doi:<https://doi.org/10.1016/j.elspec.2015.05.007>.
- [35] A. Preston, B. Ruck, L. Piper, A. DeMasi, K. Smith, A. Schleife, F. Fuchs, F. Bechstedt, J. Chai, S. Durbin, Band structure of zno from resonant x-ray emission spectroscopy, *Physical Review B* 78 (15) (2008) 155114.
- [36] A. Schleife, C. Rödl, F. Fuchs, J. Furthmüller, F. Bechstedt, Optical and energy-loss spectra of mgo, zno, and cdo from ab initio many-body calculations, *Phys. Rev. B* 80 (2009) 035112. doi:[10.1103/PhysRevB.80.035112](https://doi.org/10.1103/PhysRevB.80.035112).
- [37] A. Schleife, F. Fuchs, C. Rödl, J. Furthmüller, F. Bechstedt, Band-structure and optical-transition parameters of wurtzite mgo, zno, and cdo from quasiparticle calculations, *physica status solidi (b)* 246 (9) (2009) 2150–2153. doi:<https://doi.org/10.1002/pssb.200945204>.
- [38] P. Gori, M. Rakel, C. Cobet, W. Richter, N. Esser, A. Hoffmann, R. Del Sole, A. Cricenti, O. Pulci, Optical spectra of zno in the far ultraviolet: First-principles calculations and ellipsometric measurements, *Phys. Rev. B* 81 (2010) 125207. doi:[10.1103/PhysRevB.81.125207](https://doi.org/10.1103/PhysRevB.81.125207).
- [39] M. Ochi, R. Arita, S. Tsuneyuki, Correlated band structure of a transition metal oxide zno obtained from a many-body wave function theory, *Phys. Rev. Lett.* 118 (2017) 026402. doi:[10.1103/PhysRevLett.118.026402](https://doi.org/10.1103/PhysRevLett.118.026402).
- [40] C. A. Ataide, R. R. Pelá, M. Marques, L. K. Teles, J. Furthmüller, F. Bechstedt, Fast and accurate approximate quasiparticle band structure calculations

- of zno, cdo, and mgo polymorphs, *Phys. Rev. B* 95 (2017) 045126. doi:10.1103/PhysRevB.95.045126.
- [41] A. R. H. Preston, A. DeMasi, L. F. J. Piper, K. E. Smith, W. R. L. Lambrecht, A. Boonchun, T. Cheiwchanchamnangij, J. Arneemann, M. van Schilfgaarde, B. J. Ruck, First-principles calculation of resonant x-ray emission spectra applied to zno, *Phys. Rev. B* 83 (2011) 205106. doi:10.1103/PhysRevB.83.205106.
- [42] M. Stankovski, G. Antonius, D. Waroquiers, A. Miglio, H. Dixit, K. Sankaran, M. Giantomassi, X. Gonze, M. Côté, G.-M. Rignanese, G^0W^0 band gap of zno: Effects of plasmon-pole models, *Phys. Rev. B* 84 (2011) 241201. doi:10.1103/PhysRevB.84.241201.
- [43] X. Zhang, A. Schleife, Nonequilibrium bn-zno: Optical properties and excitonic effects from first principles, *Phys. Rev. B* 97 (2018) 125201. doi:10.1103/PhysRevB.97.125201.
- [44] M. Gajdoš, K. Hummer, G. Kresse, J. Furthmüller, F. Bechstedt, Linear optical properties in the projector-augmented wave methodology, *Phys. Rev. B* 73 (2006) 045112. doi:10.1103/PhysRevB.73.045112.
- [45] D. Fritsch, R. Schmidt-Grund, H. Schmidt, C. Herzinger, M. Grundmann, Polarization-dependent optical transitions at the fundamental band gap and higher critical points of wurtzite zno, in: NUSOD '05. Proceedings of the 5th International Conference on Numerical Simulation of Optoelectronic Devices, 2005., 2005, pp. 69–70. doi:10.1109/NUSOD.2005.1518139.
- [46] T. Akiyama, A. J. Freeman, K. Nakamura, T. Ito, Electronic structures and optical properties of GaN and ZnO nanowires from first principles, *Journal of Physics: Conference Series* 100 (5) (2008) 052056. doi:10.1088/1742-6596/100/5/052056.
- [47] D. Fritsch, H. Schmidt, R. Schmidt-Grund, M. Grundmann, Intensity of optical absorption close to the band edge in strained zno films, *Journal of the Korean Physical Society* 53 (1) (2008) 123–126.
- [48] R. Schmidt-Grund, B. Rheinländer, E. M. Kaidashev, M. Lorenz, M. Grundmann, D. Fritsch, M. M. Schubert, H. Schmidt, C. M. Herzinger, Vacuum ultraviolet dielectric function and band structure of zno, *Journal of the Korean Physical Society* 53 (1) (2008) 88–93.
- [49] Z. L. Wang, Zinc oxide nanostructures: growth, properties and applications, *Journal of Physics: Condensed Matter* 16 (25) (2004) R829–R858. doi:10.1088/0953-8984/16/25/r01.
- [50] Y. Ding, Z. L. Wang, Electron energy-loss spectroscopy study of ZnO nanobelts, *Journal of Electron Microscopy* 54 (3) (2005) 287–291.
- [51] Z. Zhang, X. Qi, J. Jian, X. Duan, Investigation on optical properties of zno nanowires by electron energy-loss spectroscopy, *Micron* 37 (3) (2006) 229–233.
- [52] R. F. Egerton, *Electron energy-loss spectroscopy in the electron microscope*, Springer Science & Business Media, 2011.
- [53] P. E. Batson, Local crystal anisotropy obtained in the small probe geometry, *Micron* 39 (6) (2008) 648–652.
- [54] F. J. García de Abajo, Optical excitations in electron microscopy, *Rev. Mod. Phys.* 82 (2010) 209–275.
- [55] C. Maciel-Escudero, A. Reyes-Coronado, Electromagnetic fields produced by a swift electron: A source of white light, *Wave Motion* 86 (2019) 137–149.
- [56] N. W. Bigelow, A. Vashillo, V. Iberi, J. P. Camden, D. J. Masiello, Characterization of the electron- and photon-driven plasmonic excitations of metal nanorods, *ACS Nano* 6 (8) (2012) 7497–7504. doi:10.1021/nn302980u.